

Use of BOF slag and blast furnace dust in asphalt concrete: an alternative for the construction of pavements

Alfonso López-Díaz ^a, Ricardo Ochoa-Díaz ^b & Gloria Elizabeth Grimaldo-León ^c

^a Grupo de Investigación en Materiales Siderúrgicos, Universidad Pedagógica y Tecnológica de Colombia, Tunja, Colombia. alfonso.lopez@uptc.edu.co

^b Grupo de Investigación y Desarrollo en Infraestructura Vial, Universidad Pedagógica y Tecnológica de Colombia, Tunja, Colombia. ricardo.ochoa@uptc.edu.co

^c Grupo de Investigación en Logística, Operaciones, Gestión y calidad, Universidad de Boyacá, Tunja, Colombia. gegrimaldo@uniboyaca.edu.co

Received: February 12th, 2018. Received in revised form: June 6th, 2018. Accepted: June 12th, 2018.

Abstract

The boom in the construction of large engineering works has boosted the demand for steel, which has generated an increase in the production of steel waste, a situation that causes environmental problems due to the accumulation and inadequate disposal of these by-products. The use of industrial waste in different processes must be focused on sustainable development and the protection of the environment. This work was developed with the objective of ratifying the use of Basic Oxygen Furnace slag (BOF) as coarse aggregate and studying the alternative of using Blast Furnace Dust (BFD) as a fine aggregate; to manufacture asphalt hot mixes for pavements as an alternative to mitigate the environmental problems derived from the accumulation of this steel waste and the exploitation of non-renewable materials, such as gravel and sand. To achieve the objective, three types of asphalt mixtures were analyzed, a mixture with conventional materials (control) and two mixtures that partially and totally replace the coarse aggregate with BOF and the fine aggregate with BFD. The design of the mixtures was made with the RAtional Methodology for COmpacted geomaterials' DEnsification and Strength Analysis (RAMCODES), which is based on the principle of the vacuum polygon. Tests were carried out to evaluate the physical characteristics and the susceptibility to water and plastic deformation of each type of mixture. The results of this study confirm the use of BOF and indicate that it is feasible to use BFD as fine aggregate to partially replace conventional aggregates in road paving.

Keywords: steel waste; BOF slag; blast furnace dust; asphalt concrete.

Uso de escoria BOF y polvo de alto horno en concretos asfálticos: una alternativa para la construcción de pavimentos

Resumen

El auge de la construcción de grandes obras de ingeniería ha impulsado la demanda por acero, lo que ha generado un incremento en la producción de residuos siderúrgicos, una situación que causa problemas ambientales debido a la acumulación y no disposición adecuada de estos subproductos. El uso de residuos industriales en diferentes procesos debe estar enfocado hacia el desarrollo sostenible y la protección del medio ambiente. Este trabajo se desarrolló con el objetivo de ratificar el uso de la escoria de horno al oxígeno (BOF) como agregado grueso y estudiar la alternativa del uso de polvo de alto horno (BFD) como agregado fino; para fabricar mezclas asfálticas en caliente para pavimentos como una alternativa para mitigar los problemas ambientales derivados de la acumulación de residuos siderúrgicos y de la explotación de materiales no renovables, como la grava y la arena. Para lograr el objetivo, se analizaron tres tipos de mezclas asfálticas, una mezcla con materiales convencionales (control) y dos mezclas sustituyendo parcial y totalmente el agregado grueso por BOF y el agregado fino por polvo de AH. El diseño de las mezclas se realizó con la metodología Ramcodes, la cual se basa en el principio del polígono de vacíos. Se realizaron ensayos para evaluar las características físicas y la susceptibilidad al agua y deformación plástica de cada tipo de mezcla. Los resultados de este estudio confirman el uso de BOF e indican que es factible el uso de BFD como agregado fino para reemplazar parcialmente los agregados convencionales en la pavimentación de carreteras.

Palabras clave: residuos siderúrgicos; escoria BOF; Polvo de alto horno; concreto asfáltico.

1. Introduction

The slag produced in the steel industries is a by-product

in the manufacture of steel. Three types of slag are known: Granulated Blast Furnace Slag (GBFS), Electric Arc Furnace (EAF) slag, and Basic Oxygen Furnace (BOF) slag [1]. The

How to cite: López-Díaz, A., Ochoa-Díaz, R. and Grimaldo-León, G., Use of BOF slag and blast furnace dust in asphalt concrete: an alternative for the construction of pavements. DYNA, 85(206), pp. 24-30, September, 2018.

BOF slag is produced during the transformation process of the pig iron coming from the steel blast furnace. The pig iron reacts with lime, silicates, aluminum oxides, manganese oxides, magnesium oxides, and ferrites depending on the quality of steel produced [2]. On the other hand, the Blast Furnace Dust (BFD) is produced during the transformation of iron ore into pig iron. In this process the iron ore, coke, and limestone are melted at a temperature of 1500 ° C. Additionally, during the manufacturing process of pig iron, gases and particulate fine material are generated, and the fine particulate material is decanted into collectors. BOF slag and BFD are produced in integrated steel mills. In Colombia, the only integrated steel mill is *Acerías Paz del Río S.A.* (located in the department of Boyacá, Colombia). This steelmaker produces approximately 50,000 tons of BOF slag and 20,000 tons of AH powder, a situation that generates a problem for the environment.

Taking into account the above, it is necessary to look for an alternative use of BOF slag and BFD. In this regard, the literature reports the use of BOF slag as aggregate in asphalt concrete or hydraulic concrete [3]. A possibility that reduces the use of non-renewable natural aggregates, such as limestone and sand, in the construction and improvement of roads, reducing the environmental impact in the construction of roads.

The use of BOF slag as coarse aggregate and BFD as fine aggregate in asphalt concrete requires knowledge of its physical and chemical characteristics. In this context, the research processes, in general, include two stages. First, the X-Ray Fluorescence characterization (XRF) of the BOF and BFD, as well as the determination of its mineralogical, chemical, and micro-topographic properties using a Scanning Electron Microscope (SEM) system. Second, the design and manufacture of mixtures that incorporate BOF and BFD applying the RAtional Methodology for COMPacted geomaterials' DEnsification and Strength Analysis (RAMCODES), seeking to obtain the basic requirements of

stability and flow, susceptibility to water, and resistance to plastic deformation of prepared mixtures. Finally, the results obtained are analyzed and used to determine the feasibility of using this steel waste in the manufacture of asphalt concrete used in road construction.

2. Materials and methodology

2.1. Materials

BOF slag and BFD were supplied by the steel mill *Acerías Paz del Río S.A.*, Fig. 1. The limestone was chosen as coarse aggregate and the sand as fine aggregate for the reference mixture. The basic physical properties of the materials used are shown in Table 1. The tests were carried out in accordance with Colombian standards INVIAS-2013 and international ASTM standards [4]. The asphalt cement used was 80/100 penetration and comes from the company *IncoAsfaltos S.A.S.* (Colombia). The results of the characterization tests were found within the limits of the specification and are shown in Table 2. The asphalt mixture chosen, for the development of the research, was a MDC-19 according to the specifications INV E-450-13, for a NT3 transit level ($ESALs > 5.0 \times 10^6$) [5].

2.2. Methodology

2.2.1. Tests for characterization of BOF and BFD

1. Chemical composition: X-ray fluorescence was used to quantitatively determine the elements in BOF and BFD.
2. Topographical information: scanning electron microscopy (SEM) was used to determine the morphology of BOF and BFD. The digital topographic images of the samples were obtained.



Figure 1. (a) BOF slag (b) BFD
Source: The authors.

Table 1.

Basic physical properties of the aggregates used (BOF, BFD, limestone and sand)

| Properties | Coarse aggregate | | Fine aggregate | | Specification | Standard |
|-------------------------------|------------------|-----------|----------------|-------|---------------|----------------|
| | BOF | Limestone | BFD | Sand | | |
| Loss Angeles Abrasion (%) | 20 | 20 | N/A | N/A | <25 | ASTM C 131 |
| Degradation (Micro-Deval) (%) | 20 | 20 | N/A | N/A | <20 | ASTM D 6928 |
| Soundness test (%) | 1.72 | 3.20 | - | 3.21 | <18 | ASTM C 88 |
| Fractured faces (%) | 91.4 | 94 | N/A | N/A | >85 | ASTM D 5821 |
| Plasticity index (%) | N/A | N/A | NP | NP | NP | ASTM D 4318 |
| Sand equivalent (%) | N/A | N/A | 93.8 | 68.5 | >50 | ASTM D 2919 |
| Gsb | 2.468 | 2.593 | 2.363 | 2.722 | - | |
| Gss | 2.564 | 2.605 | 2.496 | 2.743 | - | |
| Gsa | 2.729 | 2.625 | 2.727 | 2.779 | - | ASTM C 127/128 |
| Absorption (%) | 3.8 | 0.47 | 5.6 | 0.59 | - | |

Source: The authors

Table 2.

Basic properties of asphalt cement

| Properties | Measured values | Specification | Standard |
|--------------------------------|-----------------|---------------|-------------|
| Penetration at 25°C (0.1 mm) | 81.35 | 80 - 100 | ASTM D 5-97 |
| Ductility, 5 cm/min, 25°C (cm) | >100 | >100 | ASTM D 113 |
| Softening point (°C) | 50.5 | >45 | ASTM D 36 |
| Flashpoint (°C) | 245 | >230 | ASTM D 92 |
| Viscosity at 60°C (P) | 2336 | >1000 | ASTM D 2171 |

Source: The authors

2.2.2. Design of the Mixtures

The chosen gradation has a maximum nominal size of 19 mm and it was designed following Ramcodes design method [6]. This methodology has been successfully applied in the design and quality control of compacted soils for structural fillings and roads, as well as for the design and production control of asphalt mixtures. In the particular case of asphalt mixtures, Ramcodes has two very powerful analysis tools, which are the gradation chart [7] and the polygon of voids [8]. The gradation chart is an analytical environment in which several gradation of asphalt mixtures can be represented simultaneously. This allows to associate the different gradation to the mechanical or hydraulic responses, as well as to the production costs. An advantage that allows optimizing the use of the raw material in the production of asphalt mix. On the other hand, the polygon of voids is a fully automated graphic construction that allows an optimum content of asphalt cement to be determined based on the void specifications and the specific gravities of aggregates and asphalt cement. This method has the advantage to be verified only with the preparation and testing of three briquettes in contrast to the traditional procedures that use 12 to 15 briquettes (Superpave or Marshall, respectively). It is important to emphasize that it has been verified that the results with Ramcodes are very similar to those obtained with the Marshall methodology [9].

Three types of mixtures were initially designed. M1 mixture (control) was prepared using conventional materials (limestone as coarse aggregate and sand as fine aggregate). M2 mixture was prepared by replacing the coarse aggregate with BOF by 50% and the fine aggregate with BFD in equal proportion. M3 has 0% of natural aggregates. The work gradation for the three types of mixture is shown in Fig. 2.

The indicators that were taken into account for the design of each of the asphalt mixtures were: unit weight of the compacted mixture, stability, flow, percentage of voids with air in the mixture,

the vacuum between mineral aggregates, and voids filled with binder. The performance tests for each of the mixtures were: susceptibility to water and resistance to plastic deformation.

Susceptibility to water

The water susceptibility test using the indirect tensile test evaluates the change in tensile strength resulting from the effects of saturation and accelerated conditioning to water, on asphaltic mixtures compacted in the laboratory. The test was carried out following the procedure of standard INV E-725-13 and ASTM D4867. Six test pieces were prepared for each type of mixture, three to be tested in dry and three to be tested after partial saturation. The wet group samples were taken to a water bath for 24 hours at a temperature of 60 °C, after which time, the two groups of test pieces were immersed into a water bath at 25 °C for one hour. Indirect tensile strength was determined using equation (1).

$$R_T = \frac{2000P}{\pi h D} \quad (1)$$

Where:

R_T = Tensile strength (kPa)

P = Maximum load applied (N)

h = Thickness of the specimen (mm)

D = Diameter of the specimen (mm)

The tensile strength ratio (RRT) was calculated as the ratio of the average resistance to the tension of the water conditioned subgroup (RTH) and the average resistance to the tension of the subgroup maintained in dry (RTS), as expressed in equation (2).

$$RRT = \left[\frac{R_{TH}}{R_{TS}} \right] * 100 \quad (2)$$

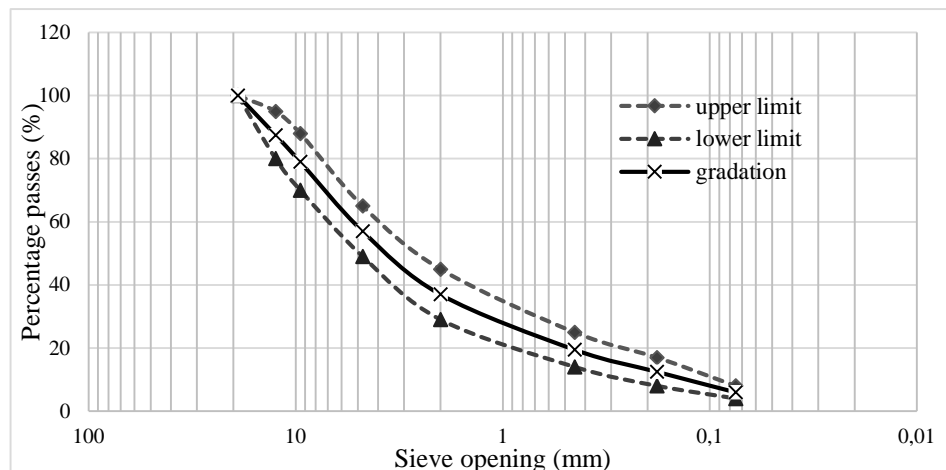


Figure 2. Working gradation for mixtures type MCD-19 according to article 450-13 INVIAS
Source: The authors.

Resistance to plastic deformation

The plastic deformation resistance test was carried out to evaluate the resistance to permanent deformation or rutting. The test was carried out in accordance with the Colombian standard INV E-756-13 and the European standard EN-12697-22, using the "Wheel Tracking Test" equipment. The test was carried out at a constant temperature of 60 °C, passing a metal wheel of 20 cm in diameter, equipped with a tread of solid rubber 5 cm wide and 2 cm thick, which exerts a contact pressure on the surface of the test piece of 900 KN/m².

The total deformations were measured in minutes 1, 3 and 5, timing from the beginning of the test. Subsequently, the deformations were measured every 5 minutes until completing 45 minutes, and from this moment, measurements were taken every 15 minutes until the end of the test at 120 minutes. From the deformations obtained at the aforementioned times, the average deformation velocity, corresponding to the time intervals, was calculated by means of equation (3).

$$V_{t2}/V_{t1} = \frac{d_{t2} - d_{t1}}{t_2 - t_1} \quad (3)$$

Where:

V_{t2}/V_{t1} = Average speed of deformation, in the time interval between t_1 y t_2 ($\mu\text{m}/\text{min}$)

d_{t1}, d_{t2} = Deformations to t_1 y t_2 respectively (μm)

t_1, t_2 = Times in the established time (min)

3. Results and discussions

3.1. Chemical components of BOF and BFD

The percentage by weight of each of the components present in the limestone and BOF slag are different, the predominant components in limestone are CaO and SiO₂ while in BOF slag are CaO and Fe₂O₃. In BFD the predominant component is Fe₂O₃ (77.5%) and in sand is SiO₂ (88.7%). BOF slag has a higher CaO/SiO₂ (4.3) ratio than the one found in limestone (3.8). BFD

has a CaO / SiO₂ ratio of 0.9 while sand ratio is 0.005, as shown in Table 3. It is important to emphasize that this ratio represents the level of alkalinity of the aggregate, and also, the presence of some high ratios lead to a stronger affinity with asphalt [10].

3.2. Microscopic morphology

Fig. 3 (a) shows the microscopic morphology of the BOF slag at a scale of 1.00KX. The microphotograph shows a rough texture and very irregular angularity, which facilitates the adherence with the asphalt. The microscopic morphology of BFD is shown in Fig. 3 (b) at a scale of 500X, in which a number of micropores are observed, which facilitates the entry of asphalt [11].

3.3. Design of the mixtures

3.3.1. Preliminary design

Initially, the granulometric dosage was made for each mixture. Next, the optimal binder content was determined with Ramcodes, taking into account the results of the characterization of the aggregates and the binder. In this methodology, an analysis of voids in the mixture is carried out: air voids (V_a), voids in the mineral aggregate (VMA) and voids filled with asphalt (VFA), which are related to the behavior of the compacted mixtures. Voids based on the percentage of binder (% Pb) and the bulk specific gravity of the mixture (G_{mb}) are represented in maps with isolines for the values allowed in the specifications (Table 4). The intersection of these lines produces a graphical construction in the space % Pb- G_{mb} , which gives rise to the polygon of voids. The centroid of the polygon establishes the optimal binder content and the specific gravity bulk (density). Fig. 4 presents the empty polygon for the mixture M2.

Following this methodology, an optimum percentage of asphalt of 5% was obtained and a density of 2.378 gr/cm³ for the mixture M1, 6.5% of asphalt and 2.375 gr/cm³ of density for the mixture M2, and 9.3% of asphalt, and 2.335 gr/cm³ of density for the M3 mixture.

Table 3.
Chemical components of BOF, limestone, BFD and sand

| Component (% in weigh) | MgO | Al ₂ O ₃ | SiO ₂ | P ₂ O ₅ | CaO | MnO | Fe ₂ O ₃ | Others |
|------------------------|------|--------------------------------|------------------|-------------------------------|-------|------|--------------------------------|--------|
| BOF | 2.70 | 4.90 | 10.80 | 2.10 | 46.80 | 2.00 | 28.80 | 1.73 |
| Limestone | 3.80 | 9.30 | 16.60 | - | 63.40 | 0.17 | 3.04 | 3.63 |
| BFD | 1.00 | 3.60 | 5.50 | 0.20 | 4.95 | 3.32 | 77.50 | 0.90 |
| Sand | 1.60 | 7.30 | 88.70 | - | 0.46 | - | 0.99 | 1.00 |

Source: The authors, based on laboratory results.

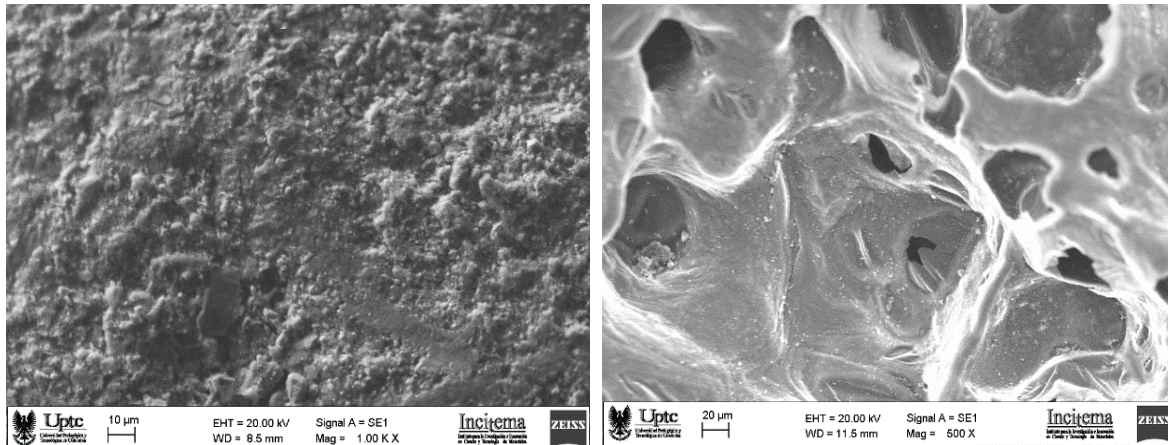


Figure 3. Microscopic morphology (a) BOF slag; (b) BFD

Source: The authors, according to tests carried out in the INCITEMA-Uptc, Tunja.

Once the optimum percentage of asphalt was determined, three test tubes of each mixture were prepared to verify compliance with the requirements established for voids in the specifications. The results are shown in Table 4.

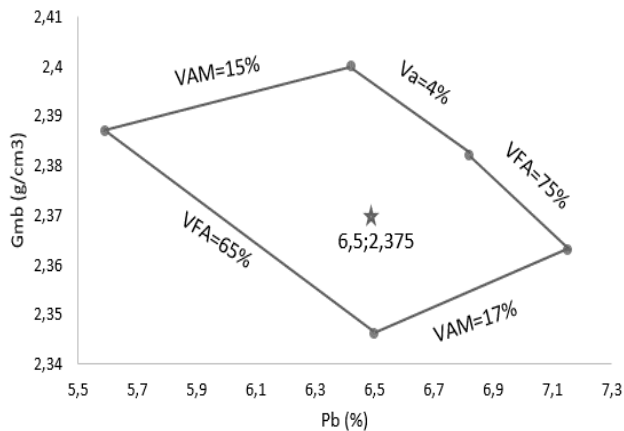


Figure 4. The polygon of voids for the M2 mixture

Source: The authors

Table 4.
Results verification of mixtures parameters

| Parameter | M1 | M2 | M3 | Specification INV E 450-13 |
|-------------|-------|-------|--------|----------------------------|
| Va, % | 4.70 | 4.70 | 4.60 | 4.0 – 6.0 |
| VMA, % min. | 15.20 | 15.51 | 15.48 | > 15 |
| VFA, % | 69.47 | 69.55 | 69.645 | 65 - 75 |

Source: The authors.

Table 5.
Results of mechanical characteristics of the mixtures

| Parameter | M1 | M2 | M3 | Specification INV E 450-13 |
|--------------|------|-------|-------|----------------------------|
| Stability, N | 9960 | 11390 | 10150 | >9000 |
| Flow, mm | 2.87 | 3.40 | 3.48 | 2.0 – 3.5 |

Source: The authors

Table 5 shows the results found in Marshall stability and flow tests. In relation to stability, the three mixtures exceed the minimum requirement of 9000 N established in the specifications of INVIAS-2013. In the case of flow, the three mixtures comply with the values of the requirement. However, M2 and M3 mixtures have higher values than M1 mixture, which is attributed to the substitution of the fine aggregate by BFD in percentages of 50 and 100%, respectively. BFD has a higher percentage of absorption (5.65%) than sand (0.59%), which allows a greater amount of asphalt for the union of the particles.

3.3.2. Performance tests

Once the working formula for each of the mixtures was obtained, the tests for the verification of the design were carried out, as well as the determination of the properties of water susceptibility and resistance to plastic deformation.

Table 6 presents the results of the RRT test performed with the specimens prepared for each type of mixture.

It was determined that the average RRT values of the different mix designs decrease as the content of BOF and BFD increases, but the minimum requirement (80%) required in the standard INV E 450-13 is achieved.

Table 6.
RTT trial results

| Condition | Id | P _{ult} (N) | RT(KPa) | RT _{ave} (KPa) | RTT _{ave} (%) |
|-----------|-----|----------------------|---------|-------------------------|------------------------|
| M1 | Wet | M1-3 | 8030 | 835.6 | 95.4 |
| | | M1-5 | 7880 | 814.8 | |
| | Dry | M1-7 | 8310 | 878.6 | |
| | | M1-8 | 8240 | 850.0 | |
| M2 | Wet | M2-2 | 4750 | 478.6 | 86.1 |
| | | M2-6 | 4680 | 471.1 | |
| | Dry | M2-7 | 5800 | 569.7 | |
| | | M2-9 | 5520 | 544.7 | |
| M3 | Wet | M3-1 | 3620 | 340.9 | 80.0 |
| | | M3-2 | 3577 | 336.9 | |
| | Dry | M3-5 | 4610 | 428.9 | |
| | | M3-6 | 4460 | 423.8 | |

Source: The authors

Fig. 5 shows the results of susceptibility testing to permanent deformation. The M1 mixture showed a maximum deformation of 1.85 mm, while M2 and M3 mixtures (modified with BOF and BFD) showed a greater deformation of 2.2 mm and 2.3 mm, respectively.

The deformation speed was calculated for the intervals between 30 - 45 minutes, 75 - 90 minutes, and 105 - 120 minutes for each of the mixtures. The results are shown in Fig. 6.

In the first interval (30 - 45 minutes) the deformation speed was very similar in the three types of mixtures. In the second interval (75 - 90 minutes) there was a greater difference between the control mixture (M1) and the modified mixtures with BOF and BFD, and the higher deformation rate was observed in the mixture M1. In the case of the third interval (105-120 minutes), like the second interval, a higher deformation speed of the mixture M1 was observed.

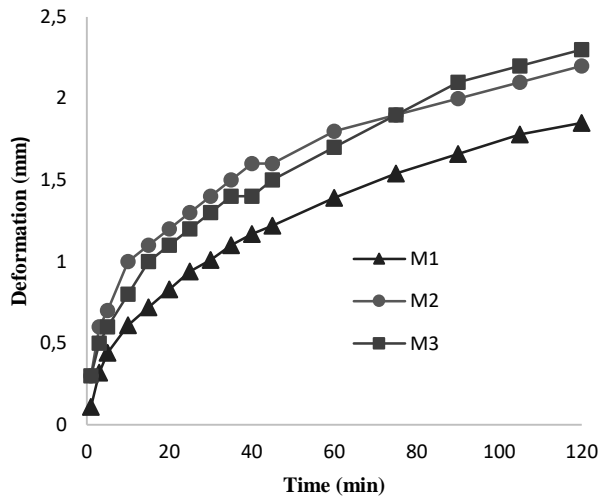


Figure 5. Evolution of deformation
Source: The authors.

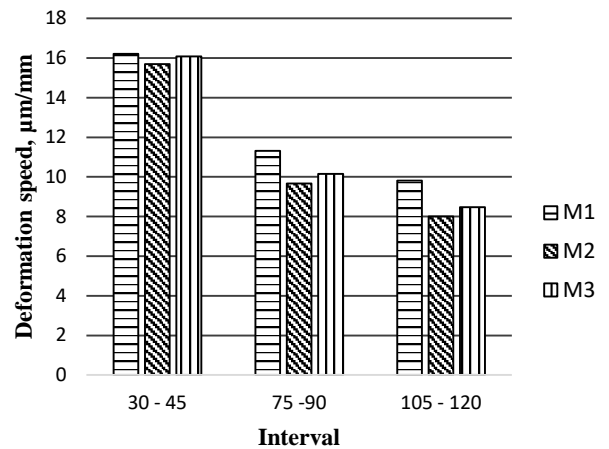


Figure 6. Deformation speed
Source: The authors.

4. Conclusions

This document studies the viability of the use of steel residues (BOF slag and BFD) as aggregates in asphalt mixtures to pave roads to generate an alternative to mitigate the environmental impact derived from the exploitation of non-renewable materials and the inadequate accumulation of this waste. For this purpose, the performance of samples of asphalt concrete was evaluated by partially and totally replacing the conventional aggregates with BOF slag and BFD. Based on the results of this study, the following conclusions are presented:

- The results of the tests to know the chemical composition of the BOF slag and BFD indicate that these materials can be used as aggregates in asphalt mixtures and do not present a risk to the environment.
- The comparison of steel residues with traditional stone aggregates shows that the CaO/SiO₂ ratio (which defines the level of alkalinity of the materials) is similar

between the BOF slag and the limestone. On the contrary, in the case of fine aggregates a difference is observed. BFD has a higher alkalinity than sand, which implies a greater affinity of this powder with the asphalt cement.

- The stability improves in the mixtures with slag BOF and BFD, the improvement in the mixture M2 with proportion 50-50 of each material being more noticeable. Likewise, an increase in the flow values was observed for modified mixtures with BOF slag and BFD, being higher in the M3 mixture prepared with 100% residues. This is due to the increase in the optimum content of asphalt cement thanks to the porous characteristics of BFD.
- The results of the RTT test indicate that the ratio between the indirect tensile strengths of the wet and dry samples decreases with the BOF slag and BFD content.
- The deformations obtained in the test of susceptibility to permanent deformation are very similar in the mixtures prepared with BOF and BFD slag. In addition, M2 and M3 mixtures present greater deformation than the control mixture, without being much superior.
- The deformation speed in the test of susceptibility to permanent deformation or rutting indicates a better behavior of the modified mixtures with the passage of time. This is due to the increase in the curing and reaction of steel waste with asphalt cement over time.
- More research should be done to evaluate the feasibility of using other types of slag (mixed or each residue individually) in asphalt mixtures or in base layers for pavements in high traffic road projects. Similarly, it is suggested that the studies include the evaluation of parameters such as resistance to permanent deformation, moisture damage, rigidity, and fatigue of the composite material.
- The results obtained in this research contribute to a better understanding of the implications of the manufacture of asphalt mixtures with unconventional materials or waste, and also, suggest that the incorporation of these waste residues are a feasible alternative for the construction of roads.
- The contribution to the environment in these types of projects focuses on reducing the use of non-renewable natural resources and the accumulation of waste to improve the environmental conditions of the areas surrounding the steel factories.

Acknowledgements

The authors thank the company *Acerías Paz del Río S.A.* for the support and supply of the materials; to the company *IncoAsfaltos S.A.S.* for the supply of asphalt cement; to the *Uptc INCITEMA*, for the development of the chemical characterization tests of the materials and, finally, to the Engineer Manuel Sierra, Coordinator of the Pavement Laboratory of *Universidad Pedagógica y Tecnológica de Colombia* (Tunja, Colombia). The Governorate of Boyacá is also thanked for their support through the COLCIENCIAS announcement 733 of 2015.

References

- [1] Kambole, A., Paige-Green, P., Kupolati, W., Ndambuki, J. and Adeboje, A., Basic oxygen furnace slag for road pavements: a review of material characteristics and performance for effective utilization in southern Africa. *Construction and Building Materials*. 148, pp. 618-631, 2017. DOI: 10.1016/j.conbuildmat.2017.05.036
- [2] Xie, J., Wu, S., Zhang, L., Xiao, Y., Liu, Q., Yang, C. and Nie, S., Material characterization and performance evaluation of asphalt mixture Incorporating basic oxygen furnace slag (BFO) sludge. *Construction and Building Materials*. 147, pp. 362-370, 2017. DOI: 10.1016/j.conbuildmat.2017.04.131
- [3] Li, Ch., Chen, Z., Wu, Sh., Li, B., Xie, J. and Xiao, Y., Effects of steel slag fillers on the rheological properties of asphalt mastic. *Construction and Building Materials*. 145, pp. 383-391, 2017. DOI: 10.1016/j.conbuildmat.2017.04.034
- [4] Instituto Nacional de Vías-INVIAS. Especificaciones generales de construcción de carreteras. 2013.
- [5] Instituto Nacional de Vías-INVIAS. Normas de ensayos de materiales para carreteras. 2013.
- [6] Sánchez-Leal, F., et al., RAMCODES: Metodología racional para el análisis de densificación y resistencia de geomateriales compactados. Descripción de la metodología y campo de aplicación. Publicación Técnica 200 ed. Sanfandila, Querétaro, México, 2002. ISSN 0188-7297.
- [7] Sánchez-Leal, F., Gradation chart for asphalt mixes: development. *Journal of Materials in Civil Engineering*. ASCE. 19(2), 2007. DOI: 10.1061/(ASCE)0899-1561(2007)19:2(185).
- [8] Sánchez-Leal, F., Anguas, P., Larreal, M. and López, D., Polyvoids: analytical tool for Superpave HMA design. *Journal of Materials in Civil Engineering* ASCE. 23(8), 2011. DOI: 10.1061/(ASCE)MT.1943-5533.0000275
- [9] Ochoa-Díaz, R., Analysis of the use of coal tar as a binder in bituminous mixtures, using Marshall and Ramcodes. *Journal of Physics: Conference Series* 466-012034, pp. 1-4, 2013. DOI: 10.1088/1742-6596/466/1/012034
- [10] Jun, X., Shaopeng, W., Juntao, L., Jun, C., Zongwu, Ch. and Wei, W., Recycling of basic oxygen furnace slag in asphalt mixture: material characterization & moisture damage investigation, *Construction and Building Materials*, 36, pp. 467-474, 2012. DOI: 10.1016/j.CONBUILDMAT.2012.06.023.
- [11] Ochoa-Díaz, R., Blast furnace dust and phosphorous slag, new materials for use in road engineering, *Journal of Physics: Conf. Series* 935- 012003, pp. 1-4, 2017. DOI: 10.1088/1742-6596/935/1/012003.

A. López-Díaz, received the BSc. in Metallurgical Engineer from the Universidad Pedagógica y Tecnológica de Colombia, Tunja, Colombia; and the PhD. in Engineering from the Rheinisch-Westfälische Technische Hochschule Aachen, Aachen, North Rhine-Westphalia, Germany. He is expert in iron and steel; professor with professional, academic and research experience in the area of steel processes. He has been the main researcher in different research projects funded by with Colciencias, Acerías Paz del Río, Diaco Gerdau and Cerromatoso.

ORCID: 0000-0002-2983-7352

R. Ochoa-Díaz, received the BSc. in Transportation and Roads Engineer and MSc. degree in Road Infrastructure, both from the Universidad Pedagógica y Tecnológica de Colombia, Tunja, Colombia. And PhD. (c) in Engineering and Materials Science at the Universidad Pedagógica y Tecnológica de Colombia, with scholarship from the Gobernación de Boyacá, in accordance with Call 733 of Colciencias 2015. He is professor with professional, academic and research experience in the area of pavements and new materials. He is active researcher of the road infrastructure research and development group, Grinfravial, at the School of Transportation and Roads Engineering the Universidad Pedagógica y Tecnológica de Colombia.

ORCID: 0000-0003-1151-7884

G.E. Grimaldo-León, received the BSc. in Industrial Production Engineer from the Universidad Francisco de Paula Santander, Colombia. MBA in Business Management from the Universidad Autónoma de Bucaramanga, Colombia. She is research professor at the Universidad de Boyacá in the area of business management and researcher of the LOGyCA research group at the Universidad de Boyacá, Colombia.

ORCID: 0000-0002-8211-4305